

Test Certificate 9912208806

Issued under Section 12 of the Standards Law, 1953

Details of order:

Order name:	Polyraz industries
Address:	Maoz Haim 10845, ISRAEL
Date order:	14-Aug-19

Sample Description As Declared:

Products:	MLPP
Sampled by:	Customer
Sample received in lab:	14-Aug-19
Testing time:	From: 15-Aug-19 to 08-Sep-19
Test requested:	Selected test(s) as requested by client
Test method:	Please refer to next page(s)
Test results:	Please refer to next page(s)

This document contains 3 pages
and may be used only in full.

The test results in this document refer only
to the item tested.

This document does not constitute a
license to mark the product with the
standards mark

Conclusion:

For compliance with EU Regulation 10/2011 as amended and Israel Standard SII 5113	
1. Overall migration of extractives from packaging using solvents simulating types of foodstuffs	Comply
2. Specific migration of heavy metals according to Regulation (EU) 10/2011	Comply
3. Specific migration of primary aromatic amines (PAA) according to Regulation (EU) 10/2011	Comply
4. U.S. Food and Drug Administration 21 CFR 175.300- "Resinous and polymeric coatings"	Comply
5. Determination of Total Lead (Pb), Cadmium (Cd), Mercury (Hg) and Hexavalent Chromium (Cr (VI)) according to European directive 94/62/EC.	Comply

Certified by:

Gadi Efrati

Head of Food Contact Material Section


Naor Cohen

Acting Head of chemistry Food and Water Branch

Date: 10/09/2019



Certificate Number: AT-2045

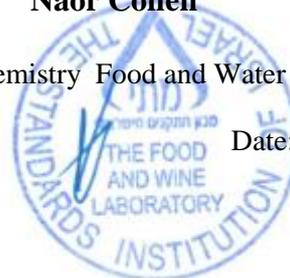

Test Certificate No.9912208806

Issued under Section 12 of the Standards Law, 1953

Description: MLPP Sheet and thermoforming products from it, PP is food contact layer.
 Aqueous and alcoholic foodstuffs, acidic, oily, milk products and dry food products for high temperature applications up to 121°C.

1- Overall Migration Protocol

Selection of test conditions as specified to Regulation 10/2011 Annex III, V;
 Selection of test method: EN 1186-1

Tested sample	Food Simulants	Test conditions	Extractives, mg/sq. dm	Limit, mg/sq. dm
MLPP	A (Ethanol 10%)	2 hours at 100°C	<1	10
MLPP	B (Acetic acid 3%)	2 hours at 100°C	<1	10
MLPP	D2 (Olive oil)	2 hours at 100°C	4.2	10

2-Specific migration of metals according to Regulation (EU) 10/2011

Selection of test method: EN 13130-1 and sample preparation in 3 w/w % acetic acid at 100°C for 2 hours
 Method: ICP-AES (inductively argon coupled plasma emission spectroscopy)

Soluble metal	SML, ppm	MDL, ppm	Results, ppm
Barium	1	0.1	ND
Cobalt	0.05	0.05	ND
Copper	5	0.1	ND
Iron	48	1	ND
Lithium	0.6	0.1	ND
Manganese	0.6	0.1	ND
Zinc	25	0.5	ND
Aluminum	1	0.1	ND
Nickel	0.02	0.01	ND

Note:

ppm=mg/kg (1,000 ppm=1,000 mg/kg=0.1%); SML = Specific Migration Limit;x
 ND= Not Detected (<MDL); MDL=Method Detection Limit;

3- Specific migration of Primary aromatic amines (PAA)- according to Regulation (EU) 10/2011

As specified in Regulation (EU) No. 10/2011 ANNEX III and V. Method: In-house method

Tested sample	Food Simulants	Test conditions	Extractives, mg/kg	Limit, mg/kg
MLPP	Acetic acid 3%	2 hours at 100°C	ND	0.01

4- Total Extractives –21 FDA 175.300

As specified in U.S Food and Drug Administration 21 FDA 175.300 table 2 condition of use: A

Tested sample	Simulants	Test conditions	Extractives, mg/in ²	Limit, mg/in ²
MLPP	Distilled water	2 hours at 250 deg. F	<0.1	0.5
MLPP	Heptane	2 hours at 150 deg. F	0.1	0.5
MLPP	Ethanol 8%	2 hours at 150 deg. F	<0.1	0.5

Test Certificate No.9912208806

Issued under Section 12 of the Standards Law, 1953

5. Lead, cadmium,mercury, hexavalent chromium Content in MLPP Sheet
Test Method :Laboratory Standard Operating Procedures in the determination of:
Lead (Pb), Cadmium (Cd), Mercury (Hg), Hexavalent Chromium (Cr (VI)) By direct X-ray Fluorescence Spectrometry (XRF) Screening.

<i>Element tested</i>	<i>Limit, ppm</i>	<i>Results, ppm</i>
<i>Lead (Pb)</i>	-	6
<i>Cadmium (Cd),</i>	-	<5
<i>Mercury (Hg)</i>	-	<5
<i>Hexavalent Chromium (Cr (VI))</i>	-	<5
<i>Sum of (Pb), (Cd), (Hg), (Cr (VI))</i>	100	<21

-End of Document-